



Review

A Unified Framework for Equivalent Single Layer Theories of Composite Beams, Plates, and Shells: a Review

Mengzhen Li^{1,2}

¹Key Laboratory of High Performance Ship Technology (Wuhan University of Technology), Ministry of Education, Wuhan, 430063, China

²School of Naval Architecture, Ocean and Energy Power Engineering, Wuhan University of Technology, Wuhan, 430063, China

Academic Editor: Dapeng Zhang <zhangdapeng@gdou.edu.cn>

Received: 01, February, 2024; Revised: 20, February, 2024; Accepted: 27, February, 2024; Published: 28, February, 2024

Abstract: This article presents a comprehensive review of the unified framework for the equivalent single layer theories of composite beams, plates and shells. First, the approach to unified displacement fields has two main categories: one is to start from the assumption of linear displacement field variables. And the another is to start from the assumption of transverse strains and transverse displacement variable. In terms of unified shape functions, the shape function is defined as the function that exist in the transverse strain rather than the in-plane displacement variables. Moreover, the basic requirements for the choose of shape functions are also given and analysed in this paper. The unified shape functions are introduced in terms of the several functions and the unified polynomial model. In addition, a construction method for new shear strain shape functions is described in this review. Finally, the current research progress and future prospects are also given.

Keywords: Unified model; Equivalent single layer theory; Composite structures

1. Introduction

The composite beams, plates and shells are the basic units of ship and marine composite structures. For example, composite laminates and sandwich panels have many advantages,

such as light weight, corrosion resistance, high strength, high damping, high designability, sound absorption, sound transmission and fatigue resistance [1–10]. Therefore, the static bending, vibration and buckling characteristics of composite beams, plates, and shells have been widely studied, and these characteristics often require the prediction of the static and dynamic characteristics of composite beams, plates, and shells by experimental, numerical, and theoretical methods.

The modeling methods of composite beams, plates and shells mainly include the three-dimensional elastic modeling method and the equivalent single layer theory. The three-dimensional elastic modeling is to discretize the displacement field of the composite plate and shell structures through the idea of finite element method and the three-dimensional representative volume elements. The static and dynamic results are calculated using suitable solution strategies. However, the three-dimensional refined modeling strategy brings high computational cost and response time, which is contrary to the concept of instantaneous prediction of structural digital twin, so the low-dimensional modeling method represented by the equivalent single layer theory has received wide attention. For composite thin plate structures, the effect of the transverse shear function on the prediction accuracy of the dynamic properties is negligible, however, for structures such as medium-thick and thick beams, plates, and shells, the transverse shear effect needs to be taken into account in order to avoid the loss of prediction accuracy. The selection of the transverse shear function is not strictly defined, as long as the free boundary conditions for shear stress are satisfied, so the selection of the transverse shear function is time-consuming and costly to be conducted.

The best-known unified method in equivalent single layer theories is the Carrera unified formulation (CUF) which is first proposed by Carrera [11]. The improved CUF theories are suitable for analyzing the global stress distribution in composite laminated structures and their applications have been presented in a large number of publications [12–31]. In 2017, Abrate and Sciuva [32] compared the existing methods to classify the displacement field based on nonpolynomials, polynomials, and the number of unknown variables. The advantage of these methods is that it is easy to classify and extend the displacement field, but the fixed form is not conducive to the discovery of specially constructed displacement fields. In 2016, Nguyen et al. [33] fit all the shear strain shape functions with a unified polynomial, and then proposed a new higher-order shear deformation theory based on the unified formula. The advantage of this method is that it can unify all the shear shape functions in a simple polynomial form but the fitting accuracy may affect the prediction accuracy. In 2020, Nguyen et al. [34] classified and summarized the existing composite beam theories and proposed a unified composite beam theory. Li et al. [4] proposed a unified composite plate theory, which classified the existing theories into three categories from the expressions of

shear strains, and new higher-order shear deformation theories can be proposed based on the unified plate theory.

This paper presents the first overview of the unified theory of composite beams, plates and shells, and the purpose of this paper is mainly to inspire the reader to construct new displacement fields through the current strategy of unified theory. This review paper is divided into four different parts. Section 1 describes some of the advantages of composite beams, plates and shells and their background in the field of marine and offshore engineering. Section 2 describes the unified displacement field and gives two different starting points for the unification of linear displacement variables and shear strains. In Section 3, the construction method of the unified shear function is presented. Section 4 summarizes recent research on the unified theory of composite beams, plates, and shells and provides guidance for future research.

2. The unified displacement fields

2.1 Starting with the displacement field variables

In terms of the kinematic assumptions, Abrate and Sciuva [32] used two broad categories (polynomials functions and non-polynomials functions) to express the displacement fields. In this paper, the displacements u and v are expanded as combined series of the transverse coordinate z . In terms of the equivalent single-layer plate theory, it is assumed that the generalized displacements (linear displacements, rotations, etc.) at each location point within the plate can be described by the reference displacements of the midplane, and reduces the computational dimensionality and the number of unknown displacement functions by the separation of variables method, which in turn improves the computational efficiency, and this method is also used in beams and shells. For example, in this section the displacements u , v , w in Cartesian system (x, y, z) are expanded into a mixed series of thickness coordinates z as follows:

$$\begin{aligned} u &= \sum_{i=0}^N u_i(x, y, t) z^i + \sum_{j=0}^N u_j(x, y, t) f_j(z) \\ v &= \sum_{i=0}^N v_i(x, y, t) z^i + \sum_{j=0}^N v_j(x, y, t) f_j(z) \\ w &= \sum_{i=0}^N w_i(x, y, t) z^i + \sum_{j=0}^N w_j(x, y, t) f_j(z) \end{aligned} \quad (1)$$

where u_i , u_j , v_i , v_j , w_i , w_j are the unknown displacement functions of the physical middle surface, independent of the thickness coordinate z . The equivalent single layer theory is usually divided into two broad categories. In the first class, the displacement field is

represented by a polynomial function in the thickness coordinate z , while in the second class, a non-polynomial function is used to describe it.

2.1.1 Polynomial displacement fields

Simple polynomials or orthogonal polynomials can be developed by expanding the displacement as a power series of the thickness coordinate z form [32]. The theory of simple polynomials is a special case of Eq. (1) when ignoring the second term in Eq. (2) is ignored.

$$u = u_i(x, y, t)z^i = u_0(x, y, t) + u_1(x, y, t)z + u_2(x, y, t)z^2 + u_3(x, y, t)z^3 + \dots$$

$$v = v_i(x, y, t)z^i = v_0(x, y, t) + v_1(x, y, t)z + v_2(x, y, t)z^2 + v_3(x, y, t)z^3 + \dots \quad (2)$$

$$w = w_i(x, y, t)z^i = w_0(x, y, t) + w_1(x, y, t)z + w_2(x, y, t)z^2 + w_3(x, y, t)z^3 + \dots$$

The above equations can theoretically be extended infinitely (the number of terms N tends to infinity). However, this gives highly computational cost due to involving in an excessive number of unknown functions and in that case, the advantage of fast operations of equivalent single-level theories would be lost. Therefore, the highest power of the power series in the above equations is often restricted for simple modeling.

For beams, only the displacement unknowns v and displacement components y are removed on the basis of the above equation, while the other terms remain unchanged, so it can be considered that the equivalent single-layer beam theory is a special case of the equivalent single-layer plate theory, as follows.

$$u = u_i(x, t)z^i = u_0(x, t) + u_1(x, t)z + u_2(x, t)z^2 + u_3(x, t)z^3 + \dots$$

$$w = w_i(x, t)z^i = w_0(x, t) + w_1(x, t)z + w_2(x, t)z^2 + w_3(x, t)z^3 + \dots \quad (3)$$

The polynomial theories are usually classified into Classical plate theory, First-order shear deformation theory, Higher order shear deformation theory), etc. Before introducing these different polynomial theories, we first The concept of $\{m, n\}$ theory is explained. The parameter m in the $\{m, n\}$ polynomial theory represents the highest order of z in the expression of the in-plane displacement variable u and the highest power of z in the expression of the variable v . The parameter n represents the highest power of z in the expression of the thickness variable w . in the polynomial theory. For example, the polynomial theory $u = u_0 + u_1z + u_2z^2$, $v = v_0 + v_1z + v_2z^2$, $w = w_0$ would be the $\{2, 0\}$ theory.

2.1.1.1 Classical plate theory

In continuum mechanics, a large number of plate and shells theories have been proposed and developed in decades. The classical plate theory is first proposed by Kirchhoff [35] in 1850 based on his assumptions and then developed by Love [36] in 1888. They assume that a

plane section normal to the mid-surface of plates remain plane and keeps normal during and after deformation and thickness of the plates does not change in this process. It is worthwhile to mention that the classical plate theory is only applicable to thin plates for the neglect of transverse shear deformation effects as well as the moment of inertia. When it comes to the moderate thick plates and thick plates, the predicted deflections are underestimated and natural frequencies and buckling loads are overestimated [37–39].

According to the displacement field listed in Eq. (2), the following strains can be obtained as

$$\begin{aligned}\varepsilon_{xz} &= \frac{\partial u}{\partial z} + \frac{\partial w}{\partial x} = \left(u_1 + \frac{\partial w_0}{\partial x}\right) + \left(2u_2 + \frac{\partial w_1}{\partial x}\right)z + \left(3u_3 + \frac{\partial w_2}{\partial x}\right)z^2 + \dots \\ \varepsilon_{yz} &= \frac{\partial v}{\partial z} + \frac{\partial w}{\partial y} = \left(v_1 + \frac{\partial w_0}{\partial y}\right) + \left(2v_2 + \frac{\partial w_1}{\partial y}\right)z + \left(3v_3 + \frac{\partial w_2}{\partial y}\right)z^2 + \dots \\ \varepsilon_{zz} &= \frac{\partial w}{\partial z} = w_1 + 2w_2z + 3w_3z^2 + \dots\end{aligned}\quad (4)$$

Based on the assumptions that the thickness of the plates does not change during and after the deformation, the strain ε_{zz} is equal to zero throughout the thickness of the plate. In that case, $w_1 = w_2 = w_3 = 0$.

In addition, it is assumed that a plane section perpendicular to the mid-surface remains plane, normal during and after deformation. Eq. (4) indicates that transverse shear strains ε_{xz} and ε_{yz} are neglected and independent of z ($\varepsilon_{xz} = \varepsilon_{yz} = 0$). Therefore, based on classical plate theory (or Kirchhoff-Love assumptions), the deformation of the plate is described as follows

$$\begin{aligned}u_1 &= -\frac{\partial w_0}{\partial x} \quad u_2 = u_3 = \dots = 0 \\ u &= u_0(x, y, t) - \frac{\partial w_0}{\partial x} z, \quad v = v_0(x, y, t) - \frac{\partial w_0}{\partial y} z, \quad w = w_0(x, y, t)\end{aligned}\quad (5)$$

2.1.1.2 The first-order shear deformation theory

The first-order shear deformation theory (also named Reissner–Mindlin plate theory) proposed by Reissner [40] and Mindlin [41] is the first and simplest theory to take into account transverse shear deformations throughout the plate thickness, it is assumed that the plane section perpendicular to the mid-surface remains plane but not necessarily perpendicular to the mid-surface, so it could be considered that this theory is also an extension of classical plate theory mentioned in the last section. Though FSDT surmounts some limitations of CPT, it also has its own drawback: the linear displacement variation throughout the thickness leads to constant transverse shear strains and stresses across the plate thickness. However, this phenomenon violates: (1) the stress-free boundary conditions on the top and bottom surface of plates; (2) parabolic distribution of transverse shear stresses

throughout the thickness. So, the integral of transverse shear stresses based on FSDT assumptions are greater than the real values, therefore, a shear correction factor (less than 1) is required to properly predict the real mechanical behavior of plates and give acceptable analytical results for moderately thick and thin plates.

In terms of the shear correction factor which should be carefully chosen in all kinds of cases, though it is hard to pick up. A constant value of $K=5/6$ is commonly used in numerical studies. Timoshenko [42] presented a shear correction coefficient which is dependent with the Poisson ratio ν .

$$K = \frac{5 + 5\nu}{6 + 5\nu} \quad (6)$$

Efraim and Eisenberger [43] then presented a shear correction factor for FGM plates as

$$K = \frac{5}{6 - (\nu_c V_c + \nu_m V_m)} \quad (7)$$

where ν_c and ν_m represent the Poisson ratios of pure ceramic and pure metal, V_c and V_m denote the volume fractions of ceramic and metal in the entire thickness of the plate.

Effects of the shear correction coefficients on the natural frequency of the FG plates is studied by Zhao et al [44]. They calculated the natural frequencies with different values of shear correction coefficients with a constant value of $5/6$, and compared those results with a HSDT results reported by Matsunaga [45]. The results show that the modified shear correction coefficients yield more accurate result than the constant value of shear correction coefficients does for a moderately thick ($a/h=10$) and thick ($a/h=5$) square FG plates. For a thin FG plate, there is no discernible differences found.

The modified first-order shear deformation theory (MFSDT) proposed by Thai et al. [46–48] is an extension of the classical first-order shear deformation plate theory. In MFSDT, the transverse displacement w is divided into bending and shear parts ($w=w_b+w_s$) and it is assumed that $\varphi_x = -w_{b,x}$, $\varphi_y = -w_{b,y}$. The following displacement field is obtained:

$$u(x,y,z)=u_0(x,y)-zw_{b,x}, v(x,y,z)=v_0(x,y)-zw_{b,y}, w(x,y,z)=w_b(x,y)+ w_s(x,y) \quad (8)$$

2.1.1.3 The second shear deformation theory

The displacement field of the second-order shear deformation theory has the highest order of two. For example, the in-plane displacement variables including linear strains and shear strain in the following equation are all quadratic.

$$u = u_0 + zu_1 + z^2u_2, v = v_0 + zv_1 + z^2v_2, w = w_0$$

$$\varepsilon_x = u_{0,x} + zu_{1,x} + z^2u_{2,x}, \varepsilon_y = v_{0,x} + zv_{1,x} + z^2v_{2,x},$$

$$\gamma_{xy} = u_{0,y} + v_{0,x} + z(u_{1,y} + v_{1,x}) + z^2(u_{2,y} + v_{2,x}), \quad (9)$$

$$\gamma_{xz}(x, y, z) = u_1 + 2zu_2 + w_{0,x}, \gamma_{yz}(x, y, z) = v_1 + 2zv_2 + w_{0,y}$$

In addition, the readers can tell from the Eq. ($\gamma_{xz} = u_1 + 2zu_2 + w_{0,x}$, $\gamma_{yz} = v_1 + 2zv_2 + w_{0,y}$) that the transverse shear stresses are linear rather than parabolic throughout the thickness. To be specific, $\gamma_{xz}(x, y, \pm h/2) = u_1 \pm hu_2 + w_{0,x}$, $\gamma_{yz}(x, y, \pm h/2) = v_1 \pm hv_2 + w_{0,y}$ are not always equal to zero unless we assume that

$$\begin{aligned} \gamma_{xz}(x, y, h/2) &= u_1 + hu_2 + w_{0,x} = 0 \\ \gamma_{xz}(x, y, -h/2) &= u_1 - hu_2 + w_{0,x} = 0 \\ \gamma_{yz}(x, y, h/2) &= v_1 + hv_2 + w_{0,y} = 0 \\ \gamma_{yz}(x, y, -h/2) &= v_1 - hv_2 + w_{0,y} = 0 \end{aligned} \quad (10)$$

In that case, $u_1 = -w_{0,x}$, $v_1 = -w_{0,y}$ and $u_2 = v_2 = 0$. Therefore, the SSDT that satisfies the stress-free boundary condition degrades to the CPT in Eq. (5). Therefore, it could be considered that the SSDT is also an extension of Kirchhoff–Love plate theory that does not take into account stress-free condition on the top and bottom surfaces of the plate.

2.1.1.4 The third-order shear deformation theory

Similar to FSDT and SSDT, the “third” in the third-order shear deformation theory refers to the highest number of in-plane transverse displacements u, v with respect to z . It can be divided into $[3, n]$ theories based on the construction of transverse displacement w , where n is the highest number of times z in transverse displacement w . For instance, in the $[3, 0]$ theory, the thickness stretching effect is not considered and $\varepsilon_{zz} = 0$. In the $[3, 1]$ theory, $\varepsilon_{zz} = w_1$ is a constant, which represents that the thickness stretching is constant throughout the thickness direction. In the $[3, 2]$ theory, $\varepsilon_{zz} = w_1 + 2zw_2$ is a constant representing that the strain is linear throughout the thickness direction. In the $[3, 3]$ theory $\varepsilon_{zz} = w_1 + 2zw_2 + 3z^2w_3$, which has a quadratic variation throughout the thickness of the beams, plates and shells. For example, Ref. [49] describes how to construct the $[3, 2]$ theory and then eliminate the redundant unknown functions by means of the stress-free condition, and finally the simplified displacement fields are obtained.

2.1.1.5 Other polynomial shear deformation theories

Other higher order shear deformation theories improve accuracy by increasing the number of displacement field variables, but also bring additional computational time.

According to the Ref. [50], the computational accuracy converges as the order increases. The fourth-order shear deformation theory is more accurate than the third-order shear deformation theory in terms of out-of-plane shear strain, but the accuracy of transverse displacement is almost the same. Therefore, higher orders are not necessary because the results obtained by the 4th order already almost overlap with the exact solution.

2.1.2 Non-polynomial displacement fields

Non-polynomial terms (such as shear functions $f(z)$ in the following equation) are introduced in the displacement fields for more accurate predicted results.

$$u = u_0 - z \frac{\partial w_0}{\partial x} + f(z)\theta_x, v = v_0 - z \frac{\partial w_0}{\partial y} + f(z)\theta_y, w = w_0 \quad (11)$$

Nonpolynomial displacement fields are often categorized by the number of unknowns and the shape of $f(z)$ [32]. The number of unknowns is not discussed in detail in this paper, and the shape of $f(z)$ is discussed will be discussed in the next section.

2.2 Starting with the transverse displacements and out-plane shear strains

Nguyen et al. [34] proposed a novel unified beam model for laminated beams and they developed a unified displacement field which can be recovered to that of existing shear deformation beam theories reported in the published literature. Only 2D shear deformation theory without thickness stretching effects is studied in Ref. [1] for simplicity.

The stress-strain relationships of the beams are given by:

$$\gamma_{xz}(x, z) = \frac{1}{G} \sigma_{xz}(x, z) \quad (12)$$

where G is shear modulus. The linear elastic relationships of strains and displacements are expressed by

$$\begin{aligned} \gamma_{xz}(x, y, z) &= \frac{\partial u}{\partial z} + \frac{\partial w}{\partial x} \\ u &= u_0 - z \frac{\partial w_0}{\partial x} + f(z) \frac{Q_x(x)}{G}, w = w_0 \end{aligned} \quad (13)$$

When $Q_x(x) = G\theta_0(x)$, $u = u_0 - zw_{0,x} + f(z)\theta_0$, $w = w_0$

When $Q_x(x) = \frac{5Gh}{6}(\theta_0(x) + w_{0,x})$, $u = u_0 + [\frac{5hf(z)}{6} - z]w_{0,x} + \frac{5hf(z)}{6}\theta_0(x)$ in Refs. [51–53].

Subsequently, Li et al. categorized the out-plane shear strains of composite plates into three types based on the existing literature. The first type contains one displacement variable Q_{1x} . The second type contains two displacement variables Q_{1x} and Q_{2x} , and the same shear

function $g(z)$. The third type contains two displacement variables and different shear strain shape functions. It is easy to notice that the third type can be used as a unified form.

$$\text{Type 1: } \gamma_{xz}(x, y, z) = \frac{\partial u}{\partial z} + \frac{\partial w}{\partial x} = g(z)Q_{1x}(x, y)$$

$$\text{Type 2: } \gamma_{xz}(x, y, z) = \frac{\partial u}{\partial z} + \frac{\partial w}{\partial x} = g(z)[Q_{1x}(x, y) + Q_{2x}(x, y)]$$

$$\text{Type 3: } \gamma_{xz}(x, y, z) = \frac{\partial u}{\partial z} + \frac{\partial w}{\partial x} = g_1(z)Q_{1x}(x, y) + g_2(z)Q_{2x}(x, y)$$

Integrating the equation in Type 3 along the thickness coordinate z yields an expression for the line displacement u . Similarly, one can integrate over γ_{yz} to obtain an expression for the line displacement v . Thus, the unified displacement fields are expressed as:

$$\begin{aligned} u &= u_0 - z \frac{\partial w}{\partial x} + f_1(z)R_{1x}(x, y) + f_2(z)R_{2x}(x, y) \\ v &= v_0 - z \frac{\partial w}{\partial y} + f_1(z)R_{1y}(x, y) + f_2(z)R_{2y}(x, y) \end{aligned} \tag{14}$$

$$w = w$$

where the transverse displacement w is user-defined and is independent of thickness coordinate z if the thickness stretching effect is ignored, and if the thickness stretching effect is considered for thick plate and shells, the transverse displacement should be expressed as a function of thickness coordinate z .

For instance, when $w = w_b$, $Q_{1x}(x, y) = \theta_x(x, y)$, the popular displacement field can be obtained [7,39,54–65] as follows.

$$u = u_0 - zw_{0,x} + f(z)\theta_x(x, y), v = v_0 - zw_{0,y} - f(z)\theta_y(x, y), w = w_0 \tag{15}$$

3. Shear strain shape functions

Many researchers used different type of shear strain shape functions (trigonometric, hyperbolic, exponential and combination) to describe shear deformation effect.

Table 1. Shear strain shape functions in different theories.

Theories	References
Trigonometric	[60] [66-72]
Hyperbolic	[55] [62] [73-76]
Exponential	[77-97]
Combination	[39] [59] [98]

In order to construct new shear strain shape functions, Li [99] proposes a construction method. First, any even function $A(z/h)$ with an independent variable z/h is given, before shifting the even function a distance of $A(0.5)$. Then, resizing the function Along the horizontal coordinate axis with a ratio of $1/[A(0)-A(0.5)]$ to satisfy the basic conditions ($f'(0) = 1$). Finally, the new shear strain shape function $f(z)$ can be obtained by integrating the scaled $f'(z)$ along the thickness direction, as shown in Fig. 1.

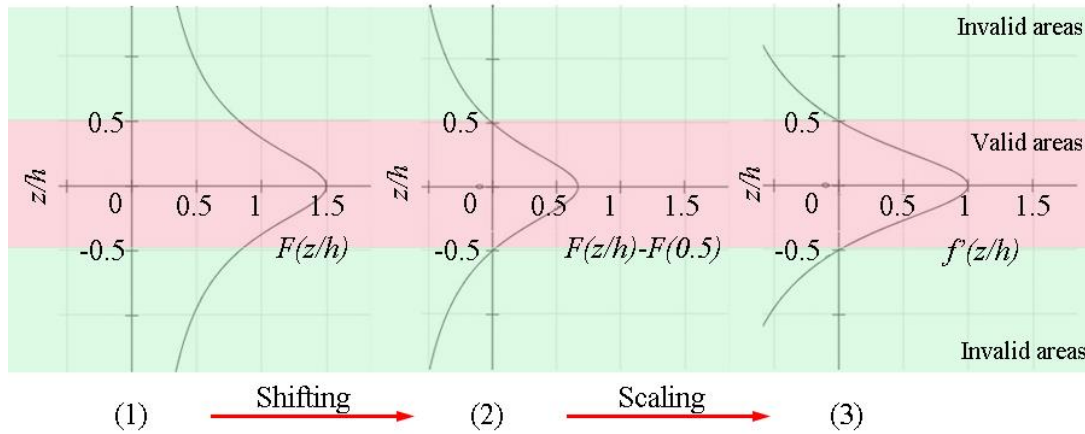


Fig. 1. The construction method for new shear shape functions [99].

To unify different types of shear strain shape functions, Nguyen et al. [33] proposed a unified polynomial formulation to unify all existing shape functions by fitting some critical points in the previous functions. However, some potential shape functions might not be easy to find due to the limit of these types of functions. Therefore, in future research, the location of these control points can be corrected using methods such as deep learning to obtain more accurate shear strain shape functions.

4. Conclusion

This review provides an overview of the unified framework of equivalent single layer theory for composite beams, plates and shells in terms of displacement fields and shear strain shape functions, respectively. This helps the readers to get more accurate displacement fields using the mentioned unified theory. For composite beams, plates and shells, traditional methods such as classical plate theory and first order shear deformation theory are sufficiently accurate. For thick ones, transverse shear effects and thickness stretching effects need to be taken into account, so more accurate equivalent single layer theories are studied. Current references focus on obtaining predictive solutions for bending, free vibration, and buckling loads and comparing them with elastic solutions to assess the accuracy of the applied theory. The literature show that the accuracies of the majority of theories are satisfactory, so further investigation is needed only for new materials and new structural forms. In addition, the fourth-order polynomial displacement field has a good convergence

and more orders are not suggested. The non-polynomial displacement field relies on the search for the shear function. However, the mathematical functions are still limited for better shear strain shape functions. Therefore, the more accurate description of the shear function may depend on the use of new technologies and methods such as machine learning.

Acknowledgments: The author would like to acknowledge the financial support from the National Natural Science Foundation of China (No. 12202324).

Conflict of interest: The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

References:

- [1] Li M, Liu Z, Yan R, Lu J, Guedes Soares C. Experimental and numerical investigation on composite single-lap single-bolt sandwich joints with different geometric parameters. *Marine Structures* 2022;85:103259. <https://doi.org/10.1016/j.marstruc.2022.103259>.
- [2] Li M, Yan R, Shen W, Qin K, Li J, Liu K. Fatigue characteristics of sandwich composite joints in ships. *Ocean Engineering* 2022;254:111254. <https://doi.org/10.1016/j.oceaneng.2022.111254>.
- [3] Li M, Zhang P, Cui J, Liu Z, Zhao Y, Qiu Y, et al. Effect of hybridization on free vibration response of Carbon/Glass hybrid composite laminates. *Journal of Reinforced Plastics and Composites* 2023;07316844231197298. <https://doi.org/10.1177/07316844231197298>.
- [4] Li M, Yan R, Xu L, Guedes Soares C. A general framework of higher-order shear deformation theories with a novel unified plate model for composite laminated and FGM plates. *Composite Structures* 2021;261:113560. <https://doi.org/10.1016/j.compstruct.2021.113560>.
- [5] Li M, Guedes Soares C, Yan R. Free vibration analysis of FGM plates on Winkler/Pasternak/Kerr foundation by using a simple quasi-3D HSDT. *Composite Structures* 2021;264:113643. <https://doi.org/10.1016/j.compstruct.2021.113643>.
- [6] Li M, Yan R, Guedes Soares C. Free vibration of advanced composite plates using a new higher order shear deformation theory. *European Journal of Mechanics - A/Solids* 2021;88:104236. <https://doi.org/10.1016/j.euromechsol.2021.104236>.
- [7] Li M, Guedes Soares C, Yan R. A novel shear deformation theory for static analysis of functionally graded plates. *Composite Structures* 2020:112559. <https://doi.org/10.1016/j.compstruct.2020.112559>.
- [8] Li M, Yan R, Shen W, Liu K. Progressive failure analysis of marine sandwich joints with a modified material degradation model. *Journal of Reinforced Plastics and Composites* 2019;38:426–38. <https://doi.org/10.1177/0731684418816383>.
- [9] Qiu Y, Yan R, Huang J, Li X, Shen W, Xu L. Progressive failure method and structural optimization analysis of marine sandwich L-shaped composite joints. *Ocean Engineering* 2023;288:116045. <https://doi.org/10.1016/j.oceaneng.2023.116045>.

- [10] Xu L, Kharghani N, Li M, Guedes Soares C. Design improvement of a composite-to-steel butt-joint based on finite element analysis. *Ocean Engineering* 2021;238:109771. <https://doi.org/10.1016/j.oceaneng.2021.109771>.
- [11] Carrera E. A class of two dimensional theories for multilayered plates analysis. *Atti Acc Sci Torino, Mem Sci Fis* 1995;19:49–87.
- [12] Iannotta DA, Giunta G, Montemurro M. A mechanical analysis of variable angle-tow composite plates through variable kinematics models based on Carrera's unified formulation. *Composite Structures* 2024;327:117717. <https://doi.org/10.1016/j.compstruct.2023.117717>.
- [13] Nicassio F, Cinefra M, Scarselli G, Filippi M, Pagani A, Carrera E. Numerical approach to disbonds in bonded composite Single Lap Joints: Comparison between Carrera Unified Formulation and classical Finite Element modeling. *Thin-Walled Structures* 2023;188:110813. <https://doi.org/10.1016/j.tws.2023.110813>.
- [14] Carrera E, Zozulya VV. Carrera Unified Formulation (CUF) for the composite plates and shells of revolution. Layer-wise models. *Composite Structures* 2024;334:117936. <https://doi.org/10.1016/j.compstruct.2024.117936>.
- [15] Foroutan K, Carrera E, Pagani A, Ahmadi H. Post-buckling and large-deflection analysis of a sandwich FG plate with FG porous core using Carrera's Unified Formulation. *Composite Structures* 2021;272:114189. <https://doi.org/10.1016/j.compstruct.2021.114189>.
- [16] Daraei B, Shojaee S, Hamzehei-Javaran S. Analysis of stationary and axially moving beams considering functionally graded material using micropolar theory and Carrera unified formulation. *Composite Structures* 2021;271:114054. <https://doi.org/10.1016/j.compstruct.2021.114054>.
- [17] De Miguel AG, Cinefra M, Filippi M, Pagani A, Carrera E. Validation of FEM models based on Carrera Unified Formulation for the parametric characterization of composite metamaterials. *Journal of Sound and Vibration* 2021;498:115979. <https://doi.org/10.1016/j.jsv.2021.115979>.
- [18] Bharati RB, Filippi M, Mahato PK, Carrera E. Flutter analysis of laminated composite structures using Carrera Unified Formulation. *Composite Structures* 2020;253:112759. <https://doi.org/10.1016/j.compstruct.2020.112759>.
- [19] Yan Y, Carrera E, Pagani A, Kaleel I, de Miguel AG. Isogeometric analysis of 3D straight beam-type structures by Carrera Unified Formulation. *Applied Mathematical Modelling* 2020;79:768–92. <https://doi.org/10.1016/j.apm.2019.11.003>.
- [20] Naderi Beni N. Free vibration analysis of annular sector sandwich plates with FG-CNT reinforced composite face-sheets based on the Carrera's Unified Formulation. *Composite Structures* 2019;214:269–92. <https://doi.org/10.1016/j.compstruct.2019.01.094>.
- [21] Ribeiro ML, Ferreira GFO, de Medeiros R, Ferreira AJM, Tita V. Experimental and numerical dynamic analysis of laminate plates via Carrera Unified Formulation. *Composite Structures* 2018;202:1176–85. <https://doi.org/10.1016/j.compstruct.2018.05.085>.

- [22] Arruda MRT, Castro LMS, Ferreira AJM, Martins D, Correia JR. Physically non-linear analysis of beam models using Carrera Unified Formulation. *Composite Structures* 2018;195:60–73. <https://doi.org/10.1016/j.compstruct.2018.03.107>.
- [23] Pagani A, Carrera E. Large-deflection and post-buckling analyses of laminated composite beams by Carrera Unified Formulation. *Composite Structures* 2017;170:40–52. <https://doi.org/10.1016/j.compstruct.2017.03.008>.
- [24] Alesadi A, Galehdari M, Shojaee S. Free vibration and buckling analysis of cross-ply laminated composite plates using Carrera's unified formulation based on Isogeometric approach. *Computers & Structures* 2017;183:38–47. <https://doi.org/10.1016/j.compstruc.2017.01.013>.
- [25] Wu B, Pagani A, Filippi M, Chen WQ, Carrera E. Large-deflection and post-buckling analyses of isotropic rectangular plates by Carrera Unified Formulation. *International Journal of Non-Linear Mechanics* 2019;116:18–31. <https://doi.org/10.1016/j.ijnonlinmec.2019.05.004>.
- [26] Alesadi A, Ghazanfari S, Shojaee S. B-spline finite element approach for the analysis of thin-walled beam structures based on 1D refined theories using Carrera unified formulation. *Thin-Walled Structures* 2018;130:313–20. <https://doi.org/10.1016/j.tws.2018.05.016>.
- [27] Naderi Beni N, Botshekanan Dehkordi M. An extension of Carrera unified formulation in polar coordinate for analysis of circular sandwich plate with FGM core using GDQ method. *Composite Structures* 2018;185:421–34. <https://doi.org/10.1016/j.compstruct.2017.11.044>.
- [28] Ramos IA, Mantari JL, Zenkour AM. Laminated composite plates subject to thermal load using trigonometrical theory based on Carrera Unified Formulation. *Composite Structures* 2016;143:324–35. <https://doi.org/10.1016/j.compstruct.2016.02.020>.
- [29] Afzali M, Farrokh M, Carrera E. Thermal buckling loads of rectangular FG plates with temperature-dependent properties using Carrera Unified Formulation. *Composite Structures* 2022;295:115787. <https://doi.org/10.1016/j.compstruct.2022.115787>.
- [30] Arruda MRT, Garrido M, Castro LMS, Ferreira AJM, Correia JR. Numerical modelling of the creep behaviour of GFRP sandwich panels using the Carrera Unified Formulation and Composite Creep Modelling. *Composite Structures* 2018;183:103–13. <https://doi.org/10.1016/j.compstruct.2017.01.074>.
- [31] Arruda MRT, Castro LMS, Ferreira AJM, Garrido M, Gonilha J, Correia JR. Analysis of composite layered beams using Carrera unified formulation with Legendre approximation. *Composites Part B: Engineering* 2018;137:39–50. <https://doi.org/10.1016/j.compositesb.2017.10.040>.
- [32] Abrate S, Di Sciuva M. Equivalent single layer theories for composite and sandwich structures: A review. *Composite Structures* 2017;179:482–94. <https://doi.org/10.1016/j.compstruct.2017.07.090>.
- [33] Nguyen TN, Thai CH, Nguyen-Xuan H. On the general framework of high order shear deformation theories for laminated composite plate structures: A novel unified approach. *International Journal of Mechanical Sciences* 2016;110:242–55. <https://doi.org/10.1016/j.ijmecsci.2016.01.012>.

- [34] Nguyen T-K, Nguyen B-D, Vo TP, Thai H-T. A novel unified model for laminated composite beams. *Composite Structures* 2020;238:111943. <https://doi.org/10.1016/j.compstruct.2020.111943>.
- [35] Kirchhoff G. Über das Gleichgewicht und die Bewegung einer elastischen Scheibe. *Journal Für Die Reine Und Angewandte Mathematik (Crelles Journal)* 1850;1850:51–88.
- [36] Love A. The Small Free Vibrations and Deformation of a Thin Elastic Shell. *Proceedings of the Royal Society of London Series I* 1887;43:352–3.
- [37] Thai H-T, Nguyen T-K, Vo TP, Ngo T. A new simple shear deformation plate theory. *Composite Structures* 2017;171:277–85. <https://doi.org/10.1016/j.compstruct.2017.03.027>.
- [38] Thai H-T, Vo TP. A new sinusoidal shear deformation theory for bending, buckling, and vibration of functionally graded plates. *Applied Mathematical Modelling* 2013;37:3269–81. <https://doi.org/10.1016/j.apm.2012.08.008>.
- [39] Thai CH, Kulasegaram S, Tran L V., Nguyen-Xuan H. Generalized shear deformation theory for functionally graded isotropic and sandwich plates based on isogeometric approach. *Computers and Structures* 2014;141:94–112. <https://doi.org/10.1016/j.compstruc.2014.04.003>.
- [40] Reissner E. The effect of transverse shear deformation on the bending of elastic plates 1945.
- [41] Mindlin R. Influence of rotatory inertia and shear on flexural motions of isotropic, elastic plates 1951.
- [42] Timoshenko SP. X. On the transverse vibrations of bars of uniform cross-section. *The London, Edinburgh, and Dublin Philosophical Magazine and Journal of Science* 1922;43:125–31.
- [43] Efraim E, Eisenberger M. Exact vibration analysis of variable thickness thick annular isotropic and FGM plates. *Journal of Sound and Vibration* 2007;299:720–38.
- [44] Zhao X, Lee Y, Liew KM. Free vibration analysis of functionally graded plates using the element-free kp-Ritz method. *Journal of Sound and Vibration* 2009;319:918–39.
- [45] Matsunaga H. Free vibration and stability of functionally graded plates according to a 2-D higher-order deformation theory. *Composite Structures* 2008;82:499–512.
- [46] Thai H-T, Choi D-H. A simple first-order shear deformation theory for the bending and free vibration analysis of functionally graded plates. *Composite Structures* 2013;101:332–40. <https://doi.org/10.1016/j.compstruct.2013.02.019>.
- [47] Thai H-T, Choi D-H. A simple first-order shear deformation theory for laminated composite plates. *Composite Structures* 2013;106:754–63. <https://doi.org/10.1016/j.compstruct.2013.06.013>.
- [48] Thai H-T, Nguyen T-K, Vo TP, Lee J. Analysis of functionally graded sandwich plates using a new first-order shear deformation theory. *European Journal of Mechanics - A/Solids* 2014;45:211–25. <https://doi.org/10.1016/j.euromechsol.2013.12.008>.
- [49] Barut A, Madenci E, Heinrich J, Tessler A. Analysis of thick sandwich construction by a {3, 2}-order theory. *International Journal of Solids and Structures* 2001;38:6063–77.

- [50] Sahraee S, Saidi A. Axisymmetric bending analysis of thick functionally graded circular plates using fourth-order shear deformation theory. *European Journal of Mechanics-A/Solids* 2009;28:974–84.
- [51] Reddy JN. A Simple Higher-Order Theory for Laminated Composite Plates. *Journal of Applied Mechanics* 1984;51:745–52. <https://doi.org/10.1115/1.3167719>.
- [52] Reissner E. On transverse bending of plates, including the effect of transverse shear deformation 1974.
- [53] Shi G, Lam K, Tay T. On efficient finite element modeling of composite beams and plates using higher-order theories and an accurate composite beam element. *Composite Structures* 1998;41:159–65.
- [54] Ai Y, Sha Y, Wang K, Shi H, Xiang S. Analysis of isotropic, sandwich and laminated plates by a meshless method and various shear deformation theories. *Composite Structures* 2009;91:31–7. <https://doi.org/10.1016/j.compstruct.2009.04.029>.
- [55] Aydogdu M. A new shear deformation theory for laminated composite plates. *Composite Structures* 2009;89:94–101. <https://doi.org/10.1016/j.compstruct.2008.07.008>.
- [56] Sobhy M. Buckling and free vibration of exponentially graded sandwich plates resting on elastic foundations under various boundary conditions. *Composite Structures* 2013;99:76–87. <https://doi.org/10.1016/j.compstruct.2012.11.018>.
- [57] Mantari JL, Oktem AS, Guedes Soares C. Bending response of functionally graded plates by using a new higher order shear deformation theory. *Composite Structures* 2012;94:714–23. <https://doi.org/10.1016/j.compstruct.2011.09.007>.
- [58] Mantari JL, Oktem AS, Guedes Soares C. A new trigonometric shear deformation theory for isotropic, laminated composite and sandwich plates. *International Journal of Solids and Structures* 2012;49:43–53. <https://doi.org/10.1016/j.ijsolstr.2011.09.008>.
- [59] Mantari JL, Oktem AS, Guedes Soares C. A new higher order shear deformation theory for sandwich and composite laminated plates. *Composites Part B: Engineering* 2012;43:1489–99. <https://doi.org/10.1016/j.compositesb.2011.07.017>.
- [60] Thai CH, Ferreira AJM, Bordas SPA, Rabczuk T, Nguyen-Xuan H. Isogeometric analysis of laminated composite and sandwich plates using a new inverse trigonometric shear deformation theory. *European Journal of Mechanics, A/Solids* 2014;43:89–108. <https://doi.org/10.1016/j.euromechsol.2013.09.001>.
- [61] Mantari JL, Bonilla EM, Guedes Soares C. A new tangential-exponential higher order shear deformation theory for advanced composite plates. *Composites Part B: Engineering* 2014;60:319–28. <https://doi.org/10.1016/j.compositesb.2013.12.001>.
- [62] Mantari JL, Granados E V., Guedes Soares C. Vibrational analysis of advanced composite plates resting on elastic foundation. *Composites Part B: Engineering* 2014;66:407–19. <https://doi.org/10.1016/j.compositesb.2014.05.026>.
- [63] Sarangan S, Singh BN. Higher-order closed-form solution for the analysis of laminated composite and sandwich plates based on new shear deformation theories. *Composite Structures* 2016;138:391–403. <https://doi.org/10.1016/j.compstruct.2015.11.049>.

- [64] Kumar R, Lal A, Singh BN, Singh J. New transverse shear deformation theory for bending analysis of FGM plate under patch load. *Composite Structures* 2019;208:91–100. <https://doi.org/10.1016/j.compstruct.2018.10.014>.
- [65] Mantari JL, Guedes Soares C. Bending analysis of thick exponentially graded plates using a new trigonometric higher order shear deformation theory. *Composite Structures* 2012;94:1991–2000. <https://doi.org/10.1016/j.compstruct.2012.01.005>.
- [66] Arya H, Shimpi R, Naik N. A zigzag model for laminated composite beams. *Composite Structures* 2002;56:21–4. [https://doi.org/10.1016/S0263-8223\(01\)00178-7](https://doi.org/10.1016/S0263-8223(01)00178-7).
- [67] Hoang VNV, Thanh PT. A new trigonometric shear deformation plate theory for free vibration analysis of FGM plates with two-directional variable thickness. *Thin-Walled Structures* 2024;194:111310. <https://doi.org/10.1016/j.tws.2023.111310>.
- [68] Levy M. Mémoire sur la théorie des plaques élastiques planes. *Journal de Mathématiques Pures et Appliquées* 1877:219–306.
- [69] Pal S, Rout M, Karmakar A. Thermoelastic free vibration analysis of functionally graded conical shell based on trigonometric higher-order shear deformation theory. *International Journal of Solids and Structures* 2023;284:112505. <https://doi.org/10.1016/j.ijsolstr.2023.112505>.
- [70] Nguyen T-K, Nguyen P, Vo T, Thai T. Vibration and buckling analysis of functionally graded sandwich beams by a new higher-order shear deformation theory. *Composites Part B: Engineering* 2015;76:273–85. <https://doi.org/10.1016/j.compositesb.2015.02.032>.
- [71] Grover N, Singh BN, Maiti DK. New nonpolynomial shear-deformation theories for structural behavior of laminated-composite and sandwich plates. *AIAA Journal* 2013;51:1861–71.
- [72] Nguyen V-H, Nguyen T-K, Thai H-T, Vo TP. A new inverse trigonometric shear deformation theory for isotropic and functionally graded sandwich plates. *Composites Part B: Engineering* 2014;66:233–46. <https://doi.org/10.1016/j.compositesb.2014.05.012>.
- [73] Shi P, Dong C. A refined hyperbolic shear deformation theory for nonlinear bending and vibration isogeometric analysis of laminated composite plates. *Thin-Walled Structures* 2022;174:109031. <https://doi.org/10.1016/j.tws.2022.109031>.
- [74] Karama M, Afaq KS, Mistou S. Mechanical behaviour of laminated composite beam by the new multi-layered laminated composite structures model with transverse shear stress continuity. *International Journal of Solids and Structures* 2003;40:1525–46.
- [75] Van Vinh P, Huy LQ. Finite element analysis of functionally graded sandwich plates with porosity via a new hyperbolic shear deformation theory. *Defence Technology* 2022;18:490–508. <https://doi.org/10.1016/j.dt.2021.03.006>.
- [76] Mantari JL, Oktem AS, Guedes Soares C. Static and dynamic analysis of laminated composite and sandwich plates and shells by using a new higher-order shear deformation theory. *Composite Structures* 2011;94:37–49. <https://doi.org/10.1016/j.compstruct.2011.07.020>.
- [77] Soldatos KP. A transverse shear deformation theory for homogeneous monoclinic plates. *Acta Mechanica* 1992;94:195–220.

- [78] Thai H-T, Vo TP, Bui TQ, Nguyen T-K. A quasi-3D hyperbolic shear deformation theory for functionally graded plates. *Acta Mechanica* 2014;225:951–64. <https://doi.org/10.1007/s00707-013-0994-z>.
- [79] Shinde B, Sayyad A, Kawade A. Thermal analysis of isotropic plates using hyperbolic shear deformation theory. *Applied and Computational Mechanics* 2013;7:193–204.
- [80] Li J, Hua H. The effects of shear deformation on the free vibration of elastic beams with general boundary conditions. *Proceedings of The Institution of Mechanical Engineers Part C-Journal of Mechanical Engineering Science* 2010;224:71–84. <https://doi.org/10.1243/09544062JMES1527>.
- [81] Li J, Shi C, Shao K, Li X, Wu W. Free vibration of axially loaded composite beams with general boundary conditions using hyperbolic shear deformation theory. *Composite Structures* 2013;97:1–14. <https://doi.org/10.1016/j.compstruct.2012.10.014>.
- [82] Sayyad A, Ghugal Y. Flexure of Thick Beams using New Hyperbolic Shear Deformation Theory. *International Journal of Mechanics* 2011;5:113–22.
- [83] Mahajan VM, Sharma A. Evaluation of static and dynamic responses considering thickness stretching effect for layered composite and sandwich arches using exponential shear and normal deformation theory. *Forces in Mechanics* 2023;12:100204. <https://doi.org/10.1016/j.finmec.2023.100204>.
- [84] El Meiche N, Tounsi A, Ziane N, Mechab I, El EA. A new hyperbolic shear deformation theory for buckling and vibration of functionally graded sandwich plate. *International Journal of Mechanical Sciences* 2011;53:237–47. <https://doi.org/10.1016/j.ijmecsci.2011.01.004>.
- [85] Nguyen T-K, Nguyen B-D. A new higher-order shear deformation theory for static, buckling and free vibration analysis of functionally graded sandwich beams. *Journal of Sandwich Structures and Materials* 2015;17:613–31. <https://doi.org/10.1177/1099636215589237>.
- [86] Akavci SS. Thermal Buckling Analysis of Functionally Graded Plates on an Elastic Foundation According to a Hyperbolic Shear Deformation Theory. *Mechanics of Composite Materials* 2014;50:197–212. <https://doi.org/10.1007/s11029-014-9407-1>.
- [87] Akavci SS, Tanrikulu AH. Buckling and free vibration analyses of laminated composite plates by using two new hyperbolic shear-deformation theories. *Mechanics of Composite Materials* 2008;44:145. <https://doi.org/10.1007/s11029-008-9004-2>.
- [88] Akavci SS. Buckling and Free Vibration Analysis of Symmetric and Antisymmetric Laminated Composite Plates on an Elastic Foundation. *Journal of Reinforced Plastics and Composites* 2007;26:1907–19. <https://doi.org/10.1177/0731684407081766>.
- [89] Akavci SS. An efficient shear deformation theory for free vibration of functionally graded thick rectangular plates on elastic foundation. *Composite Structures* 2014;108:667–76. <https://doi.org/10.1016/j.compstruct.2013.10.019>.
- [90] Benyoucef S, Mechab I, Tounsi A, Fekrar A, Hassen AA, Bedia E. Bending of thick functionally graded plates resting on Winkler–Pasternak elastic foundations. *Mechanics of Composite Materials* 2010;46:425–34. <https://doi.org/10.1007/s11029-010-9159-5>.
- [91] Mahi A, Adda Bedia EA, Tounsi A. A new hyperbolic shear deformation theory for bending and free vibration analysis of isotropic, functionally graded, sandwich and

- laminated composite plates. *Applied Mathematical Modelling* 2015;39:2489–508. <https://doi.org/10.1016/j.apm.2014.10.045>.
- [92] Grover N, Maiti DK, Singh BN. A new inverse hyperbolic shear deformation theory for static and buckling analysis of laminated composite and sandwich plates. *Composite Structures* 2013;95:667–75. <https://doi.org/10.1016/j.compstruct.2012.08.012>.
- [93] Sreehari VM, George L, Maiti D. Bending and buckling analysis of smart composite plates with and without internal flaw using an inverse hyperbolic shear deformation theory. *Composite Structures* 2015;138:64–74. <https://doi.org/10.1016/j.compstruct.2015.11.045>.
- [94] Sreehari VM, Maiti D. Buckling and post buckling analysis of laminated composite plates in hygrothermal environment using an Inverse Hyperbolic Shear Deformation Theory. *Composite Structures* 2015;129:250–5. <https://doi.org/10.1016/j.compstruct.2015.04.010>.
- [95] Grover N, Maiti D, Singh BN. An efficient C0 finite element modeling of an inverse hyperbolic shear deformation theory for the flexural and stability analysis of laminated composite and sandwich plates. *Finite Elements in Analysis and Design* 2014;80:11–22. <https://doi.org/10.1016/j.finel.2013.11.003>.
- [96] Grover N, Singh BN, Maiti D. Analytical and finite element modeling of laminated composite and sandwich plates: An assessment of a new shear deformation theory for free vibration response. *International Journal of Mechanical Sciences* 2013;67:89–99. <https://doi.org/10.1016/j.ijmecsci.2012.12.010>.
- [97] Nguyen T-K. A higher-order hyperbolic shear deformation plate model for analysis of functionally graded materials. *International Journal of Mechanics and Materials in Design* 2014;11:203–19. <https://doi.org/10.1007/s10999-014-9260-3>.
- [98] Mantari JL, Guedes Soares C. Analysis of isotropic and multilayered plates and shells by using a generalized higher-order shear deformation theory. *Composite Structures* 2012;94:2640–56. <https://doi.org/10.1016/j.compstruct.2012.03.018>.
- [99] Li M. *Modeling and Mechanical Characteristics of Functionally Graded Plates Based on High-order Shear Deformation Theory*. Wuhan University of Technology, 2021.